

AD-A044 451

AKRON UNIV OHIO INST OF POLYMER SCIENCE
ADHESION OF ELASTOMERS TO RIGID SUBSTRATES--THREE SUBSTRATES WI--ETC(U)
SEP 77 P DREYFUSS, A N GENT, M L RUNGE

F/G 11/10

N00014-76-C-0408

NL


UNCLASSIFIED

TR-1

| OF |
AD
A044451



END
DATE
FILMED
10-77
DDC



AD A 044451

OFFICE OF NAVAL RESEARCH

Contract N00014-76-C-0408

Project NR 092-555

Technical Report No. 1


ADHESION OF ELASTOMERS TO RIGID SUBSTRATES -
THREE SUBSTRATES WITH UNEXPECTEDLY HIGH ADHESION

by

P. Dreyfuss, A. N. Gent and M. L. Runge

Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

September, 1977

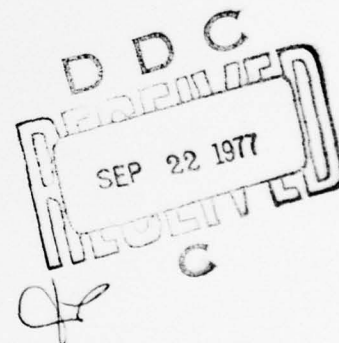

Reproduction in whole or in part is permitted
for any purpose of the United States Government

Approved for Public Release; Distribution Unlimited

AD No. _____
DDC FILE COPY

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report 1	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER 9
4. TITLE (and Subtitle) Adhesion of Elastomers to Rigid Substrates--Three Substrates with Unexpectedly High Adhesion.		5. TYPE OF REPORT & PERIOD COVERED Technical Report.
7. AUTHOR(s) P. Dreyfuss, A. N. Gent and M. L. Runge		6. PERFORMING ORG. REPORT NUMBER 15
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Science The University of Akron Akron, Ohio 44325		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0408 new
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program Arlington, Virginia 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 092-555
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 14 TR-1 12 12p.		12. REPORT DATE September 16, 1977
		13. NUMBER OF PAGES 10
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Submitted for publication in Journal of Applied Polymer Science		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Adhesion, Elastomers, Polyphenylene oxide, Polysulfone, Polycarbonate.		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) An unexpectedly high level of adhesion has been observed for simple hydrocarbon elastomers applied to certain glassy substrates: polyphenylene oxide, polysulfone and polycarbonate. The force required to separate an elastomer layer from these substrates was more than six times larger than for other glassy substrates, e.g., polystyrene and polyethyleneterephthalate. The origin of this anomalously high adhesion is not known.		

DD FORM 1473
1 JAN 73

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-LF-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

401069

JB

Adhesion of Elastomers to Rigid Substrates - Three

Substrates with Unexpectedly High Adhesion

We wish to report some initial observations on three substrates (adherends), which show unexpectedly high adhesion to simple elastomers (adhesives) under conditions where weak bonds would be anticipated; namely, low testing rates, moderate temperatures, and with the elastomer layer lightly crosslinked or physically entangled to prevent liquidlike flow (1). The data are presented in Table I along with typical results for other substrates taken from the literature and some new results with a polystyrene substrate. Clearly, the adhesion of the elastomers used here to poly-2,6-dimethyl-1,4-phenylene oxide (PPO), polysulfone, and polycarbonate is anomalously high. With these substrates cohesive failure of the elastomer occurred at high peel forces, whereas with other substrates interfacial failure was observed at low peel forces. Even in the two cases where cohesive failure was not observed with PPO, the work of adhesion was more than six times the work of adhesion for a similar polystyrene specimen.

It is interesting to speculate about why such strong bonds are formed with these three plastic substrates. One could

Section <input checked="" type="checkbox"/>	
PPO	Butt Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION CODES	
SPECIAL	
A	3

Table I

Effect of Substrate on Adhesion^a

Substrate	Elastomer ^b	Work of Adhesion(J/m ²) ^c		Ref
		50 cpm	25 cpm	
Polyethylene terephthalate ^d	SBR ^e	-	32(I)	2
	Dicup(1)	-		
	EPR ^f	-	5(I)	
Aluminum	SBR ^e	-	176(I)	2
	Dicup(1)	-		
Pyrex Glass ^g	Polybutadiene ^h	-		
	Dicup(0.05)	-	609(I)	3
	Dicup(0.2)	-	38(I)	
Quartz	Polybutadiene ^h	-		
	Dicup(0.05)	-	590(I)	3
Polystyrene ⁱ	Polybutadiene ^h	-		
	Lauroyl Peroxide(6.39)	129(I)	-	j
	Sulfur ^k	11(I)	-	
	EPR ^l	120-300(I)	-	
	SBR ^m	-	-	
PPO ⁿ	Lauroyl Peroxide(6)	150(I)	-	
	Polybutadiene ^h	-	-	
	Lauroyl Peroxide(10)	~ 500(c)	-	j
	Dicup(0.1-1)	~ 460(c)	-	
	Sulfur ^k	76(I)	-	
	EPR ^l	1200-1660(I)	-	
	SBR ^m	-	-	
	Lauroyl Peroxide(6)	> 1000(c)	-	
	Polybutadiene ^h	-	-	j
	Lauroyl Peroxide(6)	~ 500(c)	-	
Polycarbonate ^o	Polybutadiene ^h	-	-	
	Lauroyl Peroxide(6)	~ 500(c)	-	
Polysulfone ^p	Polybutadiene ^h	-	-	
	Lauroyl Peroxide(6)	~ 480(c)	-	j
	Dicup(0.1)	~ 460(c)	-	

Footnotes to Table I

- ^a Peel tests at 180° were carried out as previously described (1).
- ^b The curing agents and the percent of each are listed under the elastomer. Procedures for curing varied and are described for specific elastomer-substrate pairs.
- ^c Two speeds are given because literature data are not available at 50 cpm, where our data is most complete. We tested our samples at a variety of crosshead speeds from 0.05 cpm to 50 cpm. When cohesive failure (C) occurred at 50 cpm, it occurred at all speeds used. The differences between 50 cpm and 20 cpm were slight. I = predominantly interfacial failure. cpm = cm per min.
- ^d Mylar, Type A (E.I. du Pont de Nemours and Co.).
- ^e Ameripol 1513 (Goodrich-Gulf Chemicals, Inc.) -A 60/40: butadiene/styrene cold emulsion SBR rubber. Cured samples were prepared by swelling 1 phr Dicup and 1 phr PBNA from diethyl ether into a thin sheet of rubber, drying, and curing after bond formation for 30 min. at 150°C. Dicup=dicumyl peroxide. PBNA = phenyl-β-naphthylamine.
- ^f Vistalon 404 (Enjay Chemical Co.).
- ^g 7740 Glass (Corning Glass Works).
- ^h Diene 35 NFA (Firestone Tire and Rubber Co.) -An anionically polymerized polybutadiene rubber. Cured samples were prepared by mixing with variable amounts of peroxide on an open mill and curing after bond formation. With Dicup cures were carried out for 2 hrs. at 150°C. With lauroyl peroxide 6 hrs. at 85°C was used.
- ⁱ Styron 678 (Dow Chemical Co.).
- ^j This work.

Footnotes to Table I (contd.)

- ^k Cured samples were prepared by mixing on an open mill and curing after bonding for 9 hrs. at 65°C. The recipe contained 100 parts polybutadiene, 12 parts Butyl Eight, 1.5 parts Altax, 1.5 parts sulfur, 3 parts zinc oxide, and 0.5 parts stearic acid. Interfacial failure in these cases may be due to the presence of sulfur at the interface.
- ^l EPR 404 (Enjay Chemical Co.)
- ^m Ameripol 1502 (Goodrich-Gulf Chemicals, Inc.) -A 76.5/23.5: butadiene/styrene cold emulsion SBR rubber; cured after bond formation for 6 hrs. at 85°C.
- ⁿ (General Electric Co.)
- ^o (Cadillac Plastic and Chemical Co.)
- ^p (Scientific Polymer Products, Inc.)

suggest that chemical bonds are formed between the adherend and the adhesive during the free radical crosslinking reaction of the elastomer layer. The effect is still present, however with uncrosslinked EPR and this polymer does not contain double bonds. Furthermore, swelling in pentane for a few hours was sufficient to destroy the adhesion between crosslinked polybutadiene and both PPO and polysulfone. The corresponding adhesion to polycarbonate remained intact even after soaking in pentane for several days. It seems unlikely that the force generated on swelling a crosslinked elastomer layer would be sufficient to break chemical bonds, and we conclude that they are not formed in the cases of PPO and polysulfone, at any rate.


The structures of the three polymers have one thing in common, which, as shown in Table II, is a -O-group in the repeating unit of the backbone. Polystyrene, as is well known, has an aliphatic hydrocarbon backbone and the phenyl groups are in side chains. Possibly a specific interaction between the elastomer layer and the electron-rich backbones occurs.

Table II

Repeat Units in Substrate Backbones

<u>Substrate</u>	<u>Repeat Unit</u>
Polystyrene	$\left[\text{CH}_2 - \underset{\text{C}_6\text{H}_5}{\text{CH}} \right]_n$
PPO	$\left[\text{C}_6\text{H}_2(\text{CH}_3)_2 - \text{O} \right]_n$
Polycarbonate	$\left[\text{C}_6\text{H}_4 - \underset{\text{CH}_3}{\overset{\text{CH}_3}{\text{C}}} - \text{C}_6\text{H}_4 - \text{O} - \text{C}(=\text{O}) - \text{O} \right]_n$
Polysulfone	$\left[\text{C}_6\text{H}_4 - \text{SO}_2 - \text{C}_6\text{H}_4 - \text{O} - \text{C}_6\text{H}_4 - \underset{\text{CH}_3}{\overset{\text{CH}_3}{\text{C}}} - \text{C}_6\text{H}_4 - \text{O} \right]_n$

Alternately, the improved adhesion may be due to greater compatibility between the resins and polybutadiene, as already suggested by Iyengar and Erickson (4). Some solubility parameters, one indicator of compatibility, for the various adhesives and substrates used in this study are given in Table III. Clearly, many of the bond strengths in Table I can be reconciled with the statement that stronger bonds are formed if the solubility parameters are nearly the same. However, if indeed the solubility parameters of polystyrene and PPO are nearly identical as suggested by the authors whose data are referred to in Table III (5,6), then solubility parameter considerations cannot solely account for the observed differences in the work of adhesion between these two substrates and simple elastomers.

Finally, it should be noted that PPO and polystyrene have been shown to be compatible in all proportions (7-11). This compatibility has been attributed to "intrinsic attraction" between PPO and polystyrene. Possibly such attractive forces also exist between the three plastics showing the unexpectedly high adhesion and the rubbers bonded to them.

Work on these systems is continuing.

Table III

Solubility Parameters of Selected Polymers (12-14)

<u>Polymer</u>	<u>δ</u>
Polyethylene terephthalate	10.7
Polystyrene	9.3
Poly-2,6-dimethylphenylene oxide	9.3 ^a
Polybutadiene	8.4
EPR	7.9
SBR (60/40)	8.7
SBR (75/25)	8.6

^a Based on χ values determined by A. Schultz (5)
a private communication from W. J. MacKnight (6),
and published values of δ for polystyrene.

Acknowledgement

This work forms part of a program of research on the adhesion of elastomers supported by a research grant from the Office of Naval Research. We are indebted to A. N. Gent for helpful comments and suggestions throughout our work on the adhesion of elastomers. We also thank P. Shank of the General Electric Co. for supplying the sample of PPO and the Firestone Tire and Rubber Co. for samples of Diene 35 NFA.

References

1. A. Ahagon and A. N. Gent, J. Polym. Sci.: Polym. Phys. Ed., 13, 1285 (1975).
2. R. P. Petrich, Ph.D. Thesis, The University of Akron, 1968.
3. A. Ahagon, Ph.D. Thesis, The University of Akron, 1974.
4. Y. Iyengar and D. E. Erickson, J. Appl. Polym. Sci., 11, 2311 (1967).
5. A. R. Shultz and C. R. McCullough, J. Polym. Sci.: Polym. Phys. Ed., 10, 307 (1972).
6. W. J. MacKnight, private communication.
7. Eric P. Cizek, U. S. Patent 3,383,435 (to General Electric Co.), May 14, 1968.
8. A. F. Yee, Polym. Engineering and Science, 17, 213 (1977).
9. W. M. Prest, Jr. and R. S. Porter, J. Polym. Sci.: A-2, 10, 1639 (1972).
10. W. J. MacKnight, J. Stoelting, and F. E. Karasz, Advances in Chemistry, 99, 29 (1971).
11. J. Stoelting, F. E. Karasz, and W. J. MacKnight, Polym. Eng. Sci. 10, 133 (1970).
12. J. L. Gardon, Encyclopedia of Polym. Sci. and Technol., 3, 833 (1965).
13. "Polymer Handbook", J. Brandrup and E. H. Immergut, Interscience Publishers, J. Wiley and Sons, N.Y., 1966, p IV-358.
14. H. Burrell, Encyclopedia of Polym. Sci. and Technol., 12, 618 (1970).

M. L. Runge
P. Dreyfuss

Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

DISTRIBUTION LIST

	<u>No. Copies</u>
Office of Naval Research Code 473 Arlington, VA 22217 Attn: Dr. Miller	10
Office of Naval Research Branch Office 1030 East Green Street Pasadena, CA 91106 Attn: Dr. R. Marcus	1
Office of Naval Research Branch Office 536 S. Clark Street Chicago, IL 60605 Attn: Dr. J. Smith	1
Defense Documentation Center Bldg. 5 Cameron Station Alexandria, VA 22314	12
Office of Naval Research Branch Office 495 Summer Street Boston, MA 02210 Attn: Dr. L. H. Peebles	1
Office of Naval Research Resident Representative The Ohio State University Research Center 1314 Kinnear Road Columbus, Ohio 43212	1
U. S. Naval Research Laboratory Code 2627 Washington, DC 20375	6
U. S. Naval Research Laboratory Code 2629 Washington, DC 20375	6

Naval Research Laboratory Code 6100 Washington, DC 20375	1
Naval Air Systems Command Code 440 Washington, DC 20360 Attn: Dr. H. Rosenwasser	1
Naval Sea Systems Command SEA-0331 Washington, DC 20362 Attn: Mr. J. Murrin	1
Naval Sea Systems Command SEA-0332 Washington, DC 20362 Attn: Dr. A. Amster	1
Naval Surface Weapons Center Research and Technology Dept.-WR Silver Spring, MD 20910	1
Naval Weapons Center Research Department Code 60 China Lake, CA 93555	1
Naval Weapons Center Code 608 China Lake, CA 93555 Attn: Ronald L. Derr	3
Air Force Office of Scientific Research Directorate of Aerospace Sciences Bolling Air Force Base Washington, DC 20332	1
Air Force Office of Scientific Research Directorate of Chemical Sciences Bolling Air Force Base Washington, DC 20332	1
Air Force Office of Scientific Research Directorate of Physics Bolling Air Force Base Washington, DC 20332	1

Arnold Adicoff, Code 6058 Naval Weapons Center Research Dept. China Lake, CA 93555	(1)	R. C. Corley AFRPL/RCS Edwards, CA 93523	(1)
B. J. Alley AMSMI-RKC US AMC Redstone Arsenal, AL 35809	(1)	D. B. Davis Thiokol/Wasatch Division P.O. Box 524 Brigham City, UT 84302	(1)
Dr. S. John Bennett Thiokol Corp. Brigham City, UT 84302	(1)	John H. DeRyke Chemical Systems Div/United Technologies P.O. Box 358 Sunnyvale, CA 94088	(1)
Robert A. Biggers AFRPL/MKPB Edwards, CA 93523	(1)	James Dietz MS 243 Thiokol Corp/Wasatch Division P.O. Box 524 Brigham City, UT 84302	(1)
John E. Branigan AFRPL/RPRP Edwards, CA 93523	(1)	A. J. DiMilo Propellant R&D Aerojet General Corp. P.O. Box 15847 Sacramento, CA 95813	(1)
G. W. Burdette Code 753 Naval Weapons Center China Lake, CA 93555	(1)	R. J. DuBois Hercules Inc/Bacchus Works P.O. Box 98 - MS 8131 Magna, UT 84044	
Dr. E. A. Burns TRW Systems Bldg 0-1 Room 2020 One Space Park Redondo Beach, CA 90278	(1)	Hiram W. H. Dykes AMSMI-RKC US AMC Redstone Arsenal, AL 35809	(1)
C. D. Chandler Hercules, Inc. Radford Army Ammunition Plant Radford, VA 24141	(1)	Dr. W. David English TRW Systems Bldg 0-1, Room 2020 One Space Park Redondo Beach, CA 90278	(1)
John E. Christian Hercules/ABL P.O. Box 210 Cuberland, MD 21502	(1)	D. M. French Code 6012 Naval Ordnance Station Indian Head, MD 20640	(1)
Albert Z. Conner Hercules, Inc. Research Center Wilmington, DE 19899	(1)	W. A. Gogis, Fleet Support Naval Ordnance Station Indian Head, MD 20640	(1)

Larry H. Gordon MS 500-209
NASA/Lewis Research Center
21000 Brookpark Road
Cleveland, OH 44135

(1)

Phillip H. Graham
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

(1)

P. J. Klaas
Aerojet Solid Propulsion Co.
P.O. Box 13400
Sacramento, CA 95813

(1)

David Knoop
Olin-Energy Systems Div.
Badger Army Ammunition Plant
Baraboo, WI 53913

(1)

Joseph A. Kohlbeck, 114B
Hercules, Inc. MS 8115
Bacchus Works, P. O. Box 98
Magna, UT 84044

(1)

J. L. Koury
AFRPL/MKMB
Edwards, CA 93523

(1)

Seymour Laber
Dept. of the Army
Picatinny Arsenal, SMUPA-ADEP-2
Dover, NJ 07801

(1)

R. D. Law
Thiokol/Wasatch Division
Box 524
Brigham City, UT 84302

(1)

Dr. A. R. Lawrence
Code RM
Naval Ordnance Station
Indian Head, MD 20640

(1)

Nathan M. Liszt
SARPA-FR-G-R Bldg. 162S
Picatinny Arsenal
Feltman Res. Lab.
Dover, NJ 07801

(1)

H. E. Marsh, 125/159
Jet Propulsion Laboratory
4800 Oak Grove Drive
Pasadena, CA 91103

(1)

James D. Martin
Atlantic Research Corp.
5390 Cherokee Avenue
Alexandria, VA 22314

(1)

United Aircraft Corp/UTS
J. C. Matthews, Quality Control Lab.
1050 E. Arques Ave.
Sunnyvale, CA 94088

(1)

John O. McCary
Olin Corp - P.O. Box 222
St. Marks, FL 32355

(1)

Fred H. Meyers, Jr. MAAA
AFML, ASSB
WPAFB, OH 45433

(1)

Roy R. Miller
Hercules/ABL
P.O. Box 210
Cumberland, MD 21502

(1)

A. H. Muenker
Esso Research & Engineering
P.O. Box 8
Linden, NJ 07036

(1)

J. T. Nakamura
AFRPL/DYCA
Edwards, CA 93523

(1)

William Oetjen
Thiokol Corp/Quality Dept.
Huntsville, AL 35807

(1)

J. M. Robinson
Autonetics - Dept 646-20, Bldg. 69
3370 Miraloma Ave.
Anaheim, CA 92803

(1)

W. Roe
RPMCB
AFRPL
Edwards, CA 93523

(1)

Dr. R. E. Rogers (1)
Thiokol Corp/Development Section
Huntsville, AL 35807

T. P. Rudy. R & AT (1)
United Technology Center
P.O. Box 358
Sunnyvale, CA 94088

W. Selig (1)
Lawrence Radiation Lab - L-404
P.O. Box 808
Livermore, CA 94550

E. H. Steger (1)
Susquehanna Corp.
Atlantic Research Group
Chem. & Phys. Prop. Lab.
P.O. Box 38
Gainesville, VA 22065

Donald H. Stewart, Code 4539 (1)
Properties Analysis Branch
Naval Weapons Center
China Lake, CA 93555

Anthony Taschler (1)
Picatinny Arsenal
Products Assurance Dir.
SMUPA-QA-A-P
Dover, NJ 07801

R. J. Thiede (1)
Olin-Energy Systems Div.
Badger Army Ammunition Plant
Baraboo, WI 53913

Lewis R. Toth (1)
CIT-JPL
4800 Oak Grove Drive
Pasadena, CA 91103

J. Tuono (1)
Code 50210
Naval Ordnance Station
Indian Head, MD 20640

Norman VanderHyde (1)
AFRPL/MKPC
Edwards, CA 93523

U.S. Army Research Office (1)
Chemistry Division
P.O. Box 12211
Research Triangle Park, NC 27709

U.S. Army Research Office (1)
Physics Division
P.O. Box 12211
Research Triangle Park, NC 27709

Dr. T. J. Reinhart, Jr. Chief
Composite and Fibrous Materials
Branch
Nonmetallic Materials Division
Air Force Materials Laboratory (AFSC)
Wright-Patterson Air Force Base,
Ohio 45433 (1)